

## LASER-INDUCED DAMAGE THRESHOLD (LIDT) MEASUREMENT REPORT

### S-ON-1 (ISO 21254-2) TEST PROCEDURE

Sample: 72668 kaitintas

Request from
--------------

Address Altechna

Mokslininku st. 6A 08412 Vilnius Lithuania Aurelija Vasiljeva

Contact person Aureli

Inquiry ID 1385

Purchase order PU0020630-AVA

#### Testing institute

Address UAB Lidaris

Saulėtekio al. 10 10223 Vilnius Lithuania Lina Vigricaite 09/02/2021 SO2271 ELJVLK

#### Specimen

Tester

Test ID

Test date

Sale order

Name 72668 kaitintas

Type HR Dielectric Coating (HR (Rs>99,9%, Rp>99,7%) @ 343-355


nm, AOI 45°) Ø25.4 x 5.0 mm Plastic box

Dimensions Packaging



## TEST EQUIPMENT

#### Test setup



#### Laser and its parameters

Type Q-switched, seeded Nd:YAG

Manufacturer InnoLas Laser II

Spitlight Hybrid

Model SpitLight Hybrid

Central wavelength 355.0 nm
Angle of incidence 45.0 deg
Polarization state Linear S

Pulse repetition frequency 10 Hz Spatial beam profile in target plane TEM00

Beam diameter in target plane (1/e<sup>2</sup>) (225.8  $\pm$  2.5)  $\mu$ m

Longitudinal pulse profile Single longitudinal mode Pulse duration (EWHM)  $(5.4 \pm 0.3)$  ns

Pulse duration (FWHM)  $(5.4 \pm 0.3)$  ns Pulse to pulse energy stability (SD) 0.9 %

#### Energy/power meter

Manufacturer Ophir
Model PE50-DIF-C
Calibration due date 2021-06-01

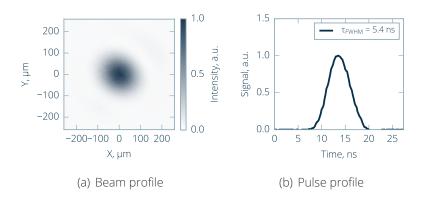


Figure 1. Laser parameters used for measurements.



### **TEST SPECIFICATION**

#### Definitions and test description

Laser-induced damage (LID) is defined as any permanent laser radiation induced change in the characteristics of the surface/bulk of the specimen which can be observed by an inspection technique and at a sensitivity related to the intended operation of the product concerned. Laser-induced damage threshold (LIDT) is defined as the highest quantity of laser radiation incident upon the optical component for which the extrapolated probability of damage is zero.

LID of the sample is investigated by performing a standardized S-on-1 test procedure.<sup>2</sup> LIDT value is determined by fitting experimental damage probability data with a model derived for a Poisson damage process assuming degenerate defect ensemble.<sup>3</sup>

Test sites	
Number of sites	210
Arrangement of sites	Hexagonal
Minimum distance between sites	750 µm
Maximum pulses per site	1000
Analysis information	
Online detection	Scattered light diode
Offline detection	Nomarski microscope
Software version	7957275 - 53e7367
Test environment	
Environment	Air
Cleanroom class (ISO 14644-1)	ISO7
Pressure	1 bar
Temperature	21.7 - 22.1 C
Humidity	11.8 - 12.6 %
Sample preparation	
Storage before test	Normal laboratory conditions
Dust blow-off	Compressed air
Cleaning	Isopropanol

<sup>&</sup>lt;sup>1</sup>ISO 21254-1:2011: Lasers and laser-related equipment - Test methods for laser-induced damage threshold - Part 1: Definitions and general principles, International Organization for Standardization, Geneva, Switzerland (2011)

FLIVLK – 72668 kaitintas

<sup>&</sup>lt;sup>2</sup>ISO 21254-2:2011: Lasers and laser-related equipment - Test methods for laser-induced damage threshold - Part 2: Threshold determination, International Organization for Standardization, Geneva, Switzerland (2011)

<sup>&</sup>lt;sup>3</sup>J. Porteus and S. Seitel, Absolute onset of optical surface damage using distributed defect ensembles, Applied Optics, 23(21), 3796–3805 (1984)



## LIDT TEST RESULTS

### LIDT VALUE

10<sup>3</sup>-on-1 4.97  $^{+0.63}_{-1.09}$  J/cm<sup>2</sup>

### CHARACTERISTIC DAMAGE CURVE

Table 1: Estimated LIDTs from fiting model for sample 72668 kaitintas.

Test mode	Threshold (Offline detection - microscopy)	Threshold (Online detection - scattering)
10-on-1	-	5.76 <sup>+1.30</sup> <sub>-1.34</sub> J/cm <sup>2</sup>
10 <sup>2</sup> -on-1	-	5.76 <sup>+0.77</sup> <sub>-1.34</sub> J/cm <sup>2</sup>
10 <sup>3</sup> -on-1	4.97 <sup>+0.63</sup> <sub>-1.09</sub> J/cm <sup>2</sup>	5.76 <sup>+0.64</sup> <sub>-1.34</sub> J/cm <sup>2</sup>

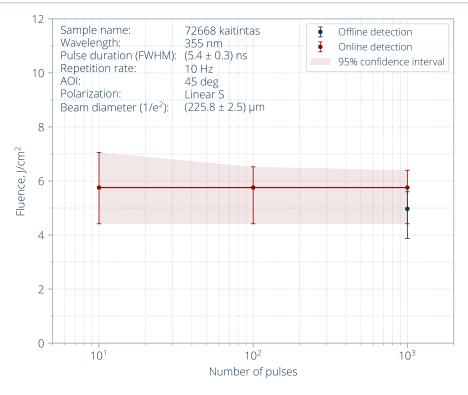


Figure 2. Characteristic damage curve.

ELJVLK – 72668 kaitintas Page 4 / 3



# DAMAGE PROBABILITY (OFFLINE DETECTION)

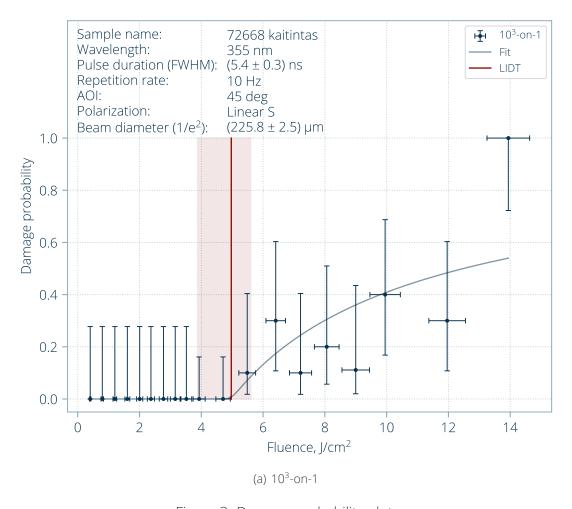


Figure 3. Damage probability plot.

ELJVLK – 72668 kaitintas Page 5 / 8



# TYPICAL DAMAGE MORPHOLOGY (OFFLINE DETECTION)



Figure 4. Typical damage morphology: fluence 5.53 J/cm<sup>2</sup>, damage after 1000 pulse(s).



Figure 5. Typical damage morphology: fluence 11.9 J/cm<sup>2</sup>, damage after 202 pulse(s).

ELJVLK – 72668 kaitintas Page 6 / 8



# DAMAGE PROBABILITY (ONLINE DETECTION)

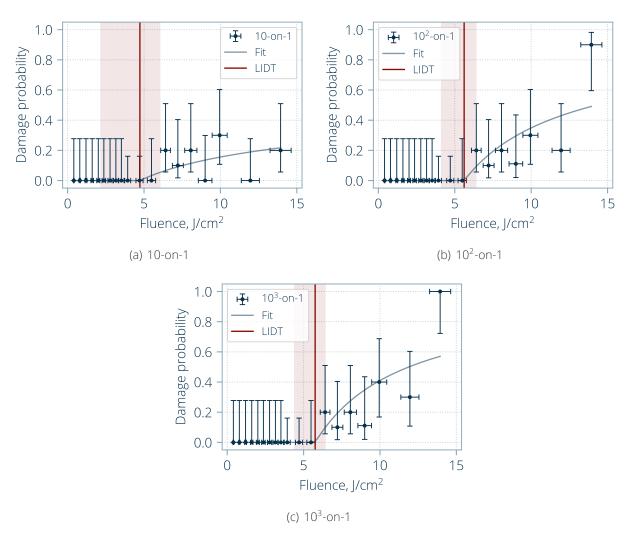


Figure 6. Damage probability plots.

ELJVLK – 72668 kaitintas Page 7 / 8



## TECHNICAL NOTES

#### **TECHNICAL NOTE 1: Oblique incidence**

According to the ISO 21254-2:2011 standard, for spatial beam profiling perpendicular to the direction of beam propagation and angles of incidence differing from 0 degrees, the cosine of the angle of incidence is included in the calculation of the effective area, which leads to correct evaluation of laser fluence at different angles of incidence (Figure 7).

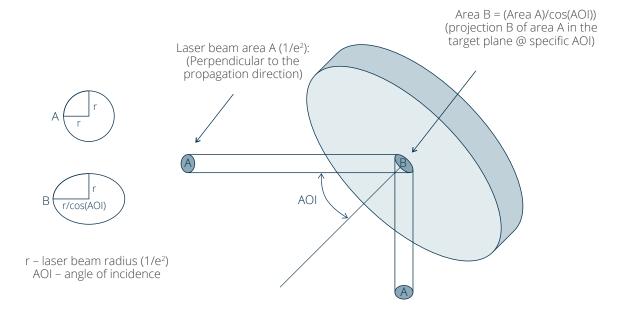


Figure 7. Oblique incidence.

ELJVLK – 72668 kaitintas Page 8 / 8